

University of Groningen

**Photodimerization of a m-phenylenebis(arylmethanofullerene): The first rigorous proof for photochemical inter-fullerene [2+2] cycloaddition**

Hummelen, J.C.; Knol, J.

*Published in:*  
Journal of the American Chemical Society

*DOI:*  
[10.1021/ja993931n](https://doi.org/10.1021/ja993931n)

**IMPORTANT NOTE: You are advised to consult the publisher's version (publisher's PDF) if you wish to cite from it. Please check the document version below.**

*Document Version*  
Publisher's PDF, also known as Version of record

*Publication date:*  
2000

[Link to publication in University of Groningen/UMCG research database](#)

*Citation for published version (APA):*

Hummelen, J. C., & Knol, J. (2000). Photodimerization of a m-phenylenebis(arylmethanofullerene): The first rigorous proof for photochemical inter-fullerene [2+2] cycloaddition: The First Rigorous Proof for Photochemical Inter-Fullerene [2 + 2] Cycloaddition. *Journal of the American Chemical Society*, 122(13), 3226 - 3227. <https://doi.org/10.1021/ja993931n>

**Copyright**

Other than for strictly personal use, it is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license (like Creative Commons).

The publication may also be distributed here under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license. More information can be found on the University of Groningen website: <https://www.rug.nl/library/open-access/self-archiving-pure/taverne-amendment>.

**Take-down policy**

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Downloaded from the University of Groningen/UMCG research database (Pure): <http://www.rug.nl/research/portal>. For technical reasons the number of authors shown on this cover page is limited to 10 maximum.

# Photodimerization of a *m*-Phenylenebis(arylmethanofullerene): The First Rigorous Proof for Photochemical Inter-Fullerene [2 + 2] Cycloaddition

Joop Knol and Jan C. Hummelen\*

Stratingh Institute and Materials Science Center  
University of Groningen, Department of Chemistry  
Nijenborgh 4, 9747 AG Groningen, The Netherlands

Received November 8, 1999

Revised Manuscript Received February 2, 2000

The functionalization of C<sub>60</sub> offers a valuable tool for obtaining new materials with special physical and electronic features. The electron-accepting and -conducting properties of the fullerene cage can be utilized in different types of molecular devices.<sup>1</sup> An example is the use of processable fullerene derivatives in bulk heterojunction photovoltaic cells in which the fullerene functions as a continuous *n*-type semiconducting network.<sup>2</sup> For optimum electron transport, the fullerene cages have to be assembled in some sort of (linear) array. Therefore, we initiated a study of functionalized molecules containing two or more C<sub>60</sub> units that can adopt conformations in which the fullerene cages are in close proximity. This type of smallest "oligomeric" C<sub>60</sub> may serve as a model for more extended fullerene arrays and clarify certain aspects of the reported behavior of C<sub>60</sub> in the solid state when exposed to light,<sup>3</sup> high pressure,<sup>4</sup> and reducing species.<sup>5</sup>

To date, several compounds incorporating two remote C<sub>60</sub> units including compounds with general structure "C<sub>60</sub>–spacer–C<sub>60</sub>" have been reported.<sup>6,7</sup> We envisaged that an appropriate choice of spacer could lead to well-defined interactions between the two independent fullerene units. On the basis of molecular models we selected a *m*-phenylenebis(methanofullerene) with general structure R–C<sub>61</sub>–(*I*,3-Ph)–C<sub>61</sub>–R as a synthetic target, since

conformational freedom allows the two fullerene cages to be in close contact.

To avoid solubility problems we prepared *m*-phenylenebis(arylmethanofullerene) **2b** carrying four solubilizing chains via a double Bamford–Stevens protocol<sup>8</sup> from bis-tosylhydrazide **1**<sup>9</sup> (Scheme 1). Reaction of **1** with sodium methoxide (1.96 equiv) in the presence of excess C<sub>60</sub> (3.6 equiv) at 70–75 °C in 1,2-dichlorobenzene (ODCB)/pyridine afforded a complex isomeric mixture (36%) containing the expected bisfulleroid **2a**. Upon heating (ODCB, reflux) the isomeric mixture was cleanly converted into the highly soluble *m*-phenylenebis(arylmethanofullerene) **2b** in 94% yield.

In contrast to the thermal behavior of **2a**, prolonged irradiation of a deoxygenated solution of **2a** (150 W sodium flood lamp) in ODCB afforded a clean steady-state mixture consisting of **2b** (~40%) and a new compound (~60%) according to HPLC and TLC analysis. Irradiation of **2b** under identical conditions gave the same result, indicating that the new compound is formed from **2b**, not **2a**. The UV–vis characteristics of the new compound, obtained from HPLC diode array detection (Figure 1), lacked any resemblance with a (mono)1,2-substituted fullerene of the type present in **2b**. Especially the weak absorption bands in the 400–800 nm region were diagnostic for a fullerene bis-addition product. On the basis of detailed studies on the regiochemistry of 2-fold additions to C<sub>60</sub> by Hirsch and co-workers,<sup>10</sup> we were able to unambiguously assign the UV–vis data to a *cis*-3 regioisomer, which is consistent with the formation of photodimer **2c** from **2b**. Structure **2c** is in full agreement with the predicted unique dimerization site for two specific (enantiotopic) *cis*-3 C=C bonds in each fullerene moiety of **2b**.<sup>11</sup> Since **2c** can be formed only as a "meso" dimer (with C<sub>s</sub> symmetry), the asymmetry of the dimerization site does not lead to two isomeric products.

Photodimer **2c** was obtained in pure form (84% based on 60% conversion) after separation from **2b** using flash chromatography with a silica gel column and CS<sub>2</sub>/toluene (90/10) as the eluent. The 500 MHz <sup>1</sup>H NMR spectrum of **2c** (Figure 2) recorded in CS<sub>2</sub> at 25 °C showed resonances for the bridging *m*-phenylene unit (8.50 (H<sub>2</sub>), 7.74 (H<sub>4</sub>, H<sub>6</sub>), and 7.29 (H<sub>5</sub>) ppm) shifted upfield with respect to **2b** (8.75 (H<sub>2</sub>), 8.12 (H<sub>4</sub>, H<sub>6</sub>), and 7.65 (H<sub>5</sub>) ppm). These shifts are probably caused by the effect of two rigidly interlocked fullerene cages in dimer **2c**.

In sharp contrast to the unsubstituted C<sub>60</sub> photodimer (C<sub>120</sub>)<sup>7d</sup> and structural analogues,<sup>7a,c,e</sup> **2c** displayed reasonable solubility in common fullerene solvents (toluene, ODCB, CS<sub>2</sub>). Hence, a <sup>13</sup>C NMR spectrum in CS<sub>2</sub> was obtained without much difficulty (Figure 3). As compared to **2b**, photodimer **2c** showed four signals for fullerene-sp<sup>3</sup> carbon atoms (δ 79.65, 74.71 (cyclopropyl) and δ 76.00, 73.14 (cyclobutyl)) and a total of 53 fullerene-sp<sup>2</sup> carbons (of a possible 56) which is in full agreement with its C<sub>s</sub> symmetry.

(7) (a) Lebedkin, S.; Ballenweg, S.; Gross, J.; Taylor, R.; Krätschmer, W. *Tetrahedron Lett.* **1995**, 36, 4971–4974. (b) Smith, A. B., III; Tokuyama, H.; Strongin, R. M.; Furst, G. T.; Romanow, W. J. *J. Am. Chem. Soc.* **1995**, 117, 9359–9360. (c) Gromov, A.; Lebedkin, S.; Ballenweg, S.; Avent, A. G.; Taylor, R.; Krätschmer, W. *Chem. Commun.* **1997**, 209–210. (d) Komatsu, K.; Wang, G.-W.; Murata, Y.; Tanaka, T.; Fujiwara, K.; Yamamoto, K.; Saunders, M. *J. Org. Chem.* **1998**, 63, 9358–9366. (e) Giesa, S.; Gross, J. H.; Hull, W. E.; Lebedkin, S.; Gromov, A.; Gleiter, R.; Krätschmer, W. *Chem. Commun.* **1999**, 465–466.

(8) (a) An, Y.-Z.; Rubin, Y.; Schaller, C.; McElvany, S. W. *J. Org. Chem.* **1994**, 59, 2927–2929. (b) Hummelen, J. C.; Knight, B. W.; LePecq, F.; Wudl, F.; Yao, J.; Wilkins, C. L. *J. Org. Chem.* **1995**, 60, 532–538.

(9) For the synthesis of **1** see Supporting Information.

(10) Djojo, F.; Herzog, A.; Lamparth, I.; Hampel, F.; Hirsch, A. *Chem. Eur. J.* **1996**, 2, 1537–1547.

(11) The *cis*-3 position as unique dimerization site in **2b** was predicted from Darling molecular models and computer-generated molecular models using Hyperchem, version 5.1. A preliminary modeling study suggests that it is hard to design other spacers (apart from *m*-phenylene) in which two parallel C=C bonds (from different C<sub>60</sub> fragments) can cyclodimerize without the introduction of a substantial amount of strain in the product.

\* Author for correspondence. E-mail: j.c.hummelen@chem.rug.nl.

(1) (a) Sariciftci, N. S.; Smilowitz, L.; Heeger, A. J.; Wudl, F. *Science* **1992**, 258, 1474–1476. (b) Sariciftci, N. S.; Braun, D.; Zhang, C.; Srdanov, V. I.; Heeger, A. J.; Stucky, G.; Wudl, F. *Appl. Phys. Lett.* **1993**, 62, 585–587. (c) Prato, M. *Top. Curr. Chem.* **1999**, 199, 173–188.

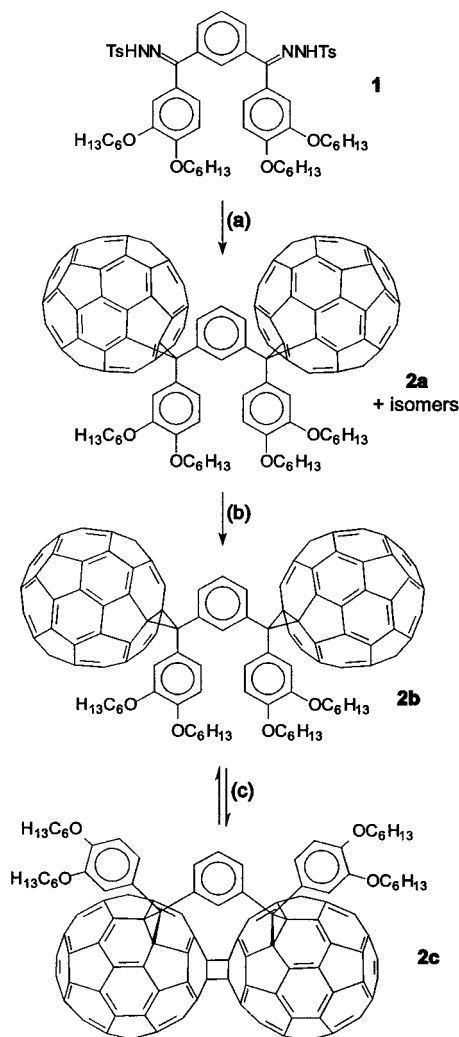
(2) Yu, G.; Gao, J.; Hummelen, J. C.; Wudl, F.; Heeger, A. J. *Science* **1995**, 270, 1789–1791.

(3) Photopolymerization of C<sub>60</sub> thin films: (a) Rao, A. M.; Zhou, P.; Wang, K.-A.; Hager, G. T.; Holden, J. M.; Wang, Y.; Lee, W.-T.; Bi, X.-X.; Eklund, P. C.; Cornett, D. S.; Duncan, M. A.; Amster, I. J. *Science* **1993**, 259, 955–957. (b) Zhou, P.; Dong, Z.-H.; Rao, A. M.; Eklund, P. C. *Chem. Phys. Lett.* **1993**, 211, 337–340. (c) Wang, Y.; Holden, J. M.; Dong, Z.-H.; Bi, X.-X.; Eklund, P. C. *Chem. Phys. Lett.* **1993**, 211, 341–345. Photopolymerization of C<sub>60</sub> in solution: (d) Sun, Y.-P.; Ma, B.; Bunker, C. E.; Liu, B. *J. Am. Chem. Soc.* **1995**, 117, 12705–12711. (e) Cataldo, F. *Polym. Int.* **1999**, 48, 143–149.

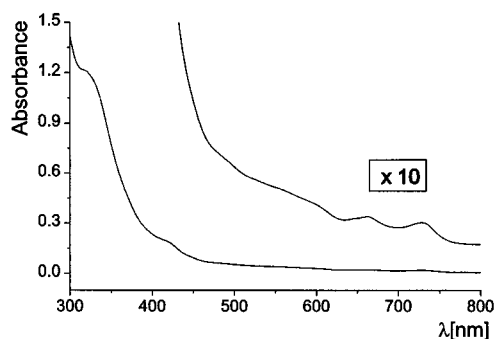
(4) Polymerization of C<sub>60</sub> under high pressure: (a) Iwasa, Y.; Arima, T.; Fleming, R. M.; Siegrist, T.; Zhou, O.; Haddon, R. C.; Rothberg, L. J.; Lyons, K. B.; Carter, H. L., Jr.; Hebard, A. F.; Tycko, R.; Dabbagh, G.; Krajewski, J. J.; Thomas, G. A.; Yagi, T. *Science* **1994**, 264, 1570–1572. (b) Núñez-Reguero, M.; Marques, L.; Hodeau, J.-L.; Béthoux, O.; Perroux, M. *Phys. Rev. Lett.* **1995**, 74, 278–281. (c) Iwasa, Y.; Tanoue, K.; Mitani, T.; Izuoka, A.; Sugawara, T.; Yagi, T. *Chem. Commun.* **1998**, 1411–1412. (d) Sundqvist, B. *Adv. Phys.* **1999**, 48, 1–134.

(5) Polymerization of reduced C<sub>60</sub>: Stephens, P. W.; Bortel, G.; Faigel, G.; Tegze, M.; Jánosy, A.; Pekker, S.; Oszlanyi, G.; Forró, L. *Nature* **1994**, 370, 636–639.

(6) Selected examples: (a) Suzuki, T.; Li, Q.; Khemani, K. C.; Wudl, F. *J. Am. Chem. Soc.* **1992**, 114, 7300–7301. (b) Diederich, F.; Dietrich-Buchecker, C.; Nierengarten, J.-F.; Sauvage, J.-P. *J. Chem. Soc., Chem. Commun.* **1995**, 781–782. (c) Lawson, J. M.; Oliver, A. M.; Rothenfluh, D. F.; An, Y.-Z.; Ellis, G. A.; Ranasinghe, M. G.; Khan, S. I.; Franz, A. G.; Ganapathi, P. S.; Shephard, M. J.; Paddon-Row, M. N.; Rubin, Y. *J. Org. Chem.* **1996**, 61, 5032–5054. (d) de Lucas, A. I.; Martín, N.; Sánchez, L.; Seoane, C. *Tetrahedron Lett.* **1996**, 37, 9391–9394. (e) Sun, Y.; Drovetskaya, T.; Bolskar, R. D.; Bau, P.; Boyd, P. D. W.; Reed, C. A. *J. Org. Chem.* **1997**, 62, 3642–3649. (f) Habicher, T.; Nierengarten, J.-F.; Gramlich, V.; Diederich, F. *Angew. Chem., Int. Ed.* **1998**, 37, 1916–1919.

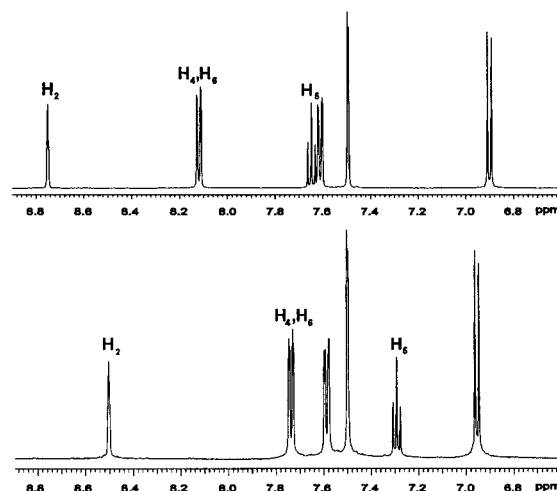
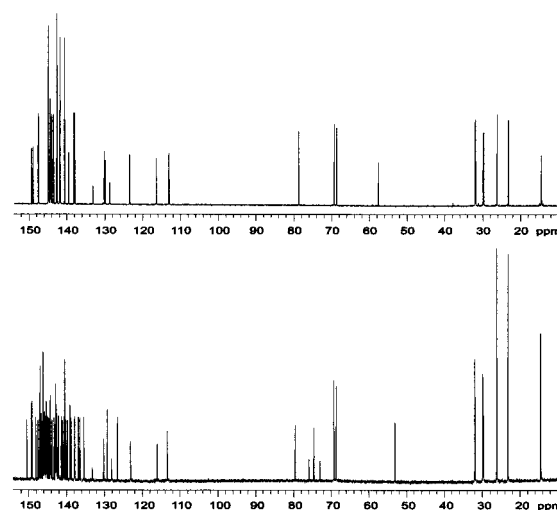
**Scheme 1.** Synthesis of *m*-Phenylenebis(arylmethanofullerene) **2b** and Photodimerization Process **2b**→**2c**<sup>a</sup>

<sup>a</sup> Reagents and conditions: (a) NaOMe, pyridine/ODCB, C<sub>60</sub>, 70–75 °C. (b) ODCB, Δ. (c) ODCB, hν, 17 °C.

**Figure 1.** UV-vis spectrum of photodimer **2c** in toluene.

The MALDI-TOF-MS data for **2c** showed the expected molecular ion with most intense peak at  $m/z = 2097.0$  ( $M + 1$ ) (calculated for <sup>12</sup>C<sub>163</sub>(<sup>13</sup>C)<sub>1</sub>H<sub>64</sub>O<sub>4</sub> ( $M + 1$ ):  $m/z = 2097.5$ ).

Control experiments showed that the photodimerization process **2b**→**2c** is significantly retarded by molecular oxygen, implying a mechanism involving the (methano)fullerene triplet excited state. A similar effect was reported for the photopolymerization process in thin solid films of C<sub>60</sub>.<sup>3a</sup> Furthermore we observed complete cycloreversion of **2c** to **2b** within 15 min in refluxing ODCB

**Figure 2.** <sup>1</sup>H NMR spectra of **2b** (top) and **2c** (bottom) recorded in CS<sub>2</sub> at 25 °C.**Figure 3.** <sup>13</sup>C NMR spectra of **2b** (top) and **2c** (bottom) recorded in CS<sub>2</sub> at 25 °C.

which is quite similar to the behavior reported for C<sub>120</sub><sup>7d</sup> and higher C<sub>60</sub> oligomers,<sup>12</sup> which revert to C<sub>60</sub> upon heating.

The three different fullerenes **2a**, **2b**, and **2c** displayed identical behavior when solutions in ODCB were irradiated for 44 h at 20 °C. In all cases mixtures of **2c/2b** of fairly identical composition (58/42 from **2a**, 61/39 from **2b**, and 61/39 from **2c**) were obtained. This confirms the reversibility of the photodimerization process **2b**→**2c**.

The synthesis of **2c** represents the first example of a controlled [2 + 2] cycloaddition process of fullerenes. It adds clear proof to long-standing proposals on structures and mechanisms involved in solid-state photo- and pressure-polymerized C<sub>60</sub>. Since [2 + 2] cycloaddition (e.g., the interconversion **2b**→**2c**) will ultimately influence the performance of devices in which the fullerene phase plays a role as electron-accepting/transporting medium, the presence of parallel oriented C=C bonds in the contact area between adjacent C<sub>60</sub> moieties has to be taken into account in the design of fullerene arrays.

**Acknowledgment.** Mr. Albert Kiewiet is acknowledged for MALDI-TOF measurements. This work was financially supported by The Netherlands' Agency for Energy and the Environment (Novem No. 146-120-008-3).

**Supporting Information Available:** Synthetic procedures and characterization data for compounds **1**, **2a**, **2b**, and **2c** (PDF). This material is available free of charge via the Internet at <http://pubs.acs.org>.

(12) Wang, Y.; Holden, J. M.; Bi, X.-X.; Ecklund, P. C. *Chem. Phys. Lett.* **1994**, *217*, 413–417.